

TOWARDS A COMPREHENSIVE STRESS-STRAIN MODEL FOR CONFINED CONCRETE COLUMNS

KARIM M. EL-DASH¹

AND

OSAMA O. EL-MAHDY²

ABSTRACT

In this paper, an analytical stress-strain model of confined concrete columns is developed and presented. The model is based on the extensively obtained data from tests of column specimens subjected to concentric compression loading. The tests included a wide range of varieties including both normal and high-strength concretes. The cross sections of the columns were of circular, rectangular, or elliptical shapes. The model incorporates the effective relevant parameters of confinement that have been observed to play important roles in confined column behavior like concrete strength, yield strength of transverse reinforcement, spacing between lateral confining element, and dimensional configuration of column specimen and its transverse reinforcement. The model can be used for concrete confined by spirals, rectilinear hoops, crossties, steel tubes of circular and rectangular cross sections, and combinations of these reinforcements.

The model demonstrates good predictive capability for concrete columns of compressive strength ranging from 20 MPa to 120 MPa. Also the model is shown to be applicable for a wide range of quantity and configuration of lateral reinforcement with volumetric ratio to concrete from 0.2% to 4%. The proposed model was compared with the existing experimental results. The comparison showed that the predicted stress-strain relationship obtained using the proposed model provides fine agreement with experimental results with respect to all considered parameters.

Keywords: Model; confined; concrete; columns; ductility; high-strength; stress-strain.

¹ Assistant Professor at Faculty of Engineering at Shobra, Zagazig University, Cairo, Egypt

² Associate Professor at Faculty of Engineering at Shobra, Zagazig University, Cairo, Egypt

INTRODUCTION

Behavior of confined concrete members has been studied extensively in the last two decades. The effect of lateral reinforcement is not considered up to 40-50% of the concrete maximum capacity, which is the actual working range. The real contribution of confinement takes place at higher range of loading when the lateral strains of concrete become high. The lateral dilation of concrete forces the lateral confining elements to stretch outside producing excessive internal strains and stresses. This behavior from the concrete towards the confining elements attracts passive pressure that enhances the strength and ductility of concrete [Van Mier (1986), Karabinis and Kiousis (1994), and Cusson and Paultre (1995)].

Behavior of concrete under concentric compressive load is governed by bond stresses between the paste and aggregates. When the applied load approaches the ultimate capacity of concrete, slippage between paste and aggregates occurs. This slippage is accompanied by crack initiation that propagates with the incremental increase of loading. If excessive lateral pressure is applied to the concrete, the contact bond will be stronger and the slippage between paste and aggregates will be delayed to a higher range of loading. When the confining reinforcement is sufficient to resume tolerable confining stress, the propagation of cracks will be slower than propagation of cracks for unconfined concrete. The slower rate of propagation causes the better ductility behavior obtained for confined concrete under compressive loading [Van Mier (1986)].

In the current study, it is targeted to establish a comprehensive stress-strain relationship of confined concrete columns subjected to concentric compressive load. The model considers columns confined by spirals, ties with/without cross ties, and concrete-filled steel tube CFST. The presented analytical relationship considers columns made by concrete with compressive strength starting with conventional strength of 20 MPa up to high compressive strength of 124 MPa. The cross sections of the columns employed were of circular, rectangular, or elliptical shapes. The model incorporates the effective relevant parameters of confinement that have been observed to play important roles in confined column behavior like concrete strength, yield strength of transverse reinforcement, spacing between lateral confining element, and dimensional configuration of column specimen and its transverse reinforcement.

The peak strength and peak strain of the stress-strain relationship are presented in a comparative study for different confinement situations. The ascending and descending branches of the stress-strain curve are incorporated in a single equation to produce a single expression for the overall needed relationship. It is targeted in the study to introduce a simple comparative model that predicts, in a high capacity, the anticipated strength and ductility enhancements due to lateral confinement. The model is applicable for concrete columns of compressive strength ranging from 20 MPa to 120 MPa. Also the model is shown to be applicable for a wide range of quantity and configuration of lateral reinforcement with volumetric ratio to concrete from 0.2% to 4%.

PREVIOUS ANALYTICAL MODELS

Many proposals were introduced to represent the stress-strain relationship of confined concrete columns. Some of these models were based on analytical derivations with subsidiary experimental support. Other models were based on the experimental investigations carried out by the authors of the same study. Most of these models lack the needed comprehensiveness

that provide the model with the capacity to represent different types of concrete columns with wide range of concrete strength, dimensional relationships, and lateral reinforcement configurations. In the following session the latest sound models and their implementation are presented.

Karabinis and Kiouisis (1994) used the theory of plasticity and the deformation compatibility equations to evaluate the development of lateral confinement of rectangular concrete columns and the resulting increase in strength and ductility. Concrete was modeled as an elastoplastic, strain hardening/softening material, with stress path dependent strength and a nonassociative flow rule. The solution is based on the coupling of the elastoplastic relations for concrete and steel, and the compatibility of deformation of the concrete core and the transverse reinforcements.

Liu and Foster (1998) presented a finite-element method to investigate the response of concentrically loaded columns with concrete strengths up to 100 MPa. The model concerned main two statements: 1) for confined high-strength concrete columns, the tie steel is not at yield at the peak load; and 2) tension strains at the cover-core interface of high-strength concrete columns are large enough to account for the early cover spalling. To investigate the mechanics of cover spalling, another finite-element model was developed by **Foster et al. (1998)**. Cover spalling was simulated by setting the elastic modulus of the cover elements to a low value once a threshold tension strain is reached at the cover-core interface, with the threshold tension strain chosen to match experimentally recorded axial strain data.

Mau et al. (1998) presented a linear-elastic solution for circular columns laterally confined by hoops. An effective confining stress at any point and an average confining factor for circular transverse cross section were defined. The relationship between the average confining factor and the longitudinal spacing of hoops was established from the numerical results of the analytical solution. The same procedure was applied through a series of finite-element analyses to square columns transversely reinforced with welded-wire-fabrics.

Few numerical models were introduced in the last decade to simulate the behavior of confined concrete. **Cusson and Paultre (1995)** developed a model based on test results of fifty high-strength confined concrete columns of square cross section with strengths from 60 MPa to 120 MPa. The experiments conducted in two different studies. The model utilized two different equations for the ascending and descending branches of the stress-strain relationship. The ascending branch represented by the following equations;

$$f_c = f_{cc} \left[\frac{k(\varepsilon_c / \varepsilon_{cc})}{k-1 + (\varepsilon_c / \varepsilon_{cc})^k} \right], \quad (1)$$

$$k = \frac{E_c}{E_c - (f_{cc} / \varepsilon_{cc})}, \quad (2)$$

while the descending branch is represented by the following equations;

$$f_c = f_{cc} \cdot \exp[k_1(\varepsilon_c - \varepsilon_{cc})^{k_2}], \quad (3)$$

$$k_1 = \frac{\ln 0.5}{(\varepsilon_{30} - \varepsilon_{cc})^{k_2}}, \quad (4)$$

$$k_2 = 0.58 + 16(f_1 / f_{cc})^{1.4} \quad (5)$$

Another model was introduced by **Hoshikuma et al. (1997)** based on the results of a series of compression loading tests of reinforced concrete column specimens. The specimens had

circular, square, and wall-type cross-sections, with various arrangements of hoop reinforcement. An equivalent confined section was also proposed to evaluate effect of cross ties in wall-type cross section. The model employed the following equation for the ascending branch;

$$f_c = f_{cc} \left[\frac{2\varepsilon_c}{\varepsilon_{cc}} - \left(\frac{\varepsilon_c}{\varepsilon_{cc}} \right)^2 \right], \quad (6)$$

and the following equation for the falling branch;

$$f_c = f_{cc} - E_{des} (\varepsilon_c - \varepsilon_{cc}) \quad (7)$$

while E_{des} is the deterioration rate and expressed by;

$$E_{des} = \frac{11.2}{\rho_{st} f_{yt} / f_{co}^2}. \quad (8)$$

Saatcioglu participated in developing and updating another numerical model starting from late 1980s. In 1999, Razvi and Saatcioglu published the last update based on 46 tests for confined concrete specimens with strengths from 60 MPa to 124 MPa. The study included 124 tests of high-strength concrete columns conducted by others and supplementary 96 additional column tests conducted using normal-strength concrete. The model utilized the following equation for the ascending branch of the stress-strain relationship;

$$f_c = \frac{f_{cc} \left(\frac{\varepsilon_c}{\varepsilon_{cc}} \right)^r}{r - 1 + \left(\frac{\varepsilon_c}{\varepsilon_{cc}} \right)^r} \quad (9)$$

where $E_c = E_c / (E_c - E_p)$. The descending branch was a linear relationship depending on the lateral confinement of the specimen. This model neglected the effect of concrete compressive strength on the strength enhancement due to confinement despite it was considered in the mathematical calculation of the strain at maximum confined strength.

ANALYTICAL MODEL

In the presented model, a fractional equation is used to predict the stress-strain relationship of laterally confined concrete. This equation has been used by Sargin et al. (1971), Ahmad and Shah (1982), and Martinez et al. (1984) to predict the stress-strain curve for different types of columns. The equation is given by;

$$y = \frac{Ax + (B-1)x^2}{1 + (A-2)x + Bx^2} \quad (10)$$

where; $y = f_c / f_{cc}$, $x = \varepsilon_c / \varepsilon_{cc}$, $A = E_c / E_p$,

f_c is the confined concrete stress at strain of ε_c , and f_{cc} and ε_{cc} are the peak stress and the corresponding strain.

The parameter A controls the slope of the ascending branch of the curve depending on the modulus of elasticity, E_c , that is calculated as per ACI-318 (1995) equation;

$$E_c = 0.036w_c^{1.5} \sqrt{f_c'} \quad (11)$$

where w_c is the unit weight of concrete in kg/m³ and f_c' is in MPa.

The ascending branch is finished at the peak point that provides the model with plastic modulus, E_p , expressed as;

$$E_p = f_{cc} / \varepsilon_{cc} \quad (12)$$

The parameter B , which primarily controls the shape of the stress-strain curve in the post-peak portion, is determined by establishing the strain of one representative point in the post-peak portion of the curve. This point used to be at 85% of the peak stress on the descending branch with the corresponding strain denoted as; ε_{85} . For high-strength concrete, the stress-strain relationship is very sensitive in the post-peak portion. The representative point chosen for strain in the post-peak portion is at 50% of the maximum stress, ε_{50} . The 50% strength post-peak point gives a good representation for the shape of post-peak portion of the curve. It is an intermediate location on the descending portion, far from the sensitivity zone near the peak point, and ahead of the tail end of the curve. This point was utilized by Cusson and Paultre (1994) in the test measurements and in their analytical model (1995). In Equation (10), when $x > 1$, the value of y should not be less than 0.2.

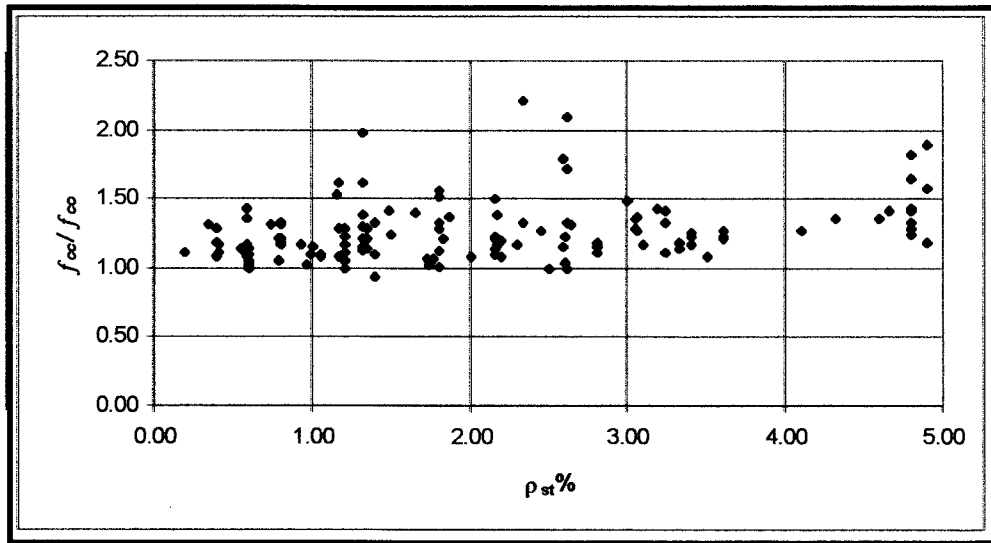


Figure 1: Relationship between volumetric ratio of lateral reinforcement, $\rho_{st}\%$, and compressive strength enhancement, f_{cc}/f_{co} .

To predict the peak stress and the corresponding strain, the following formulations are utilized;

$$f_{cc} = f_{co} + \Delta f_c \quad (13)$$

and

$$\varepsilon_{cc} = \varepsilon_{co} + \Delta \varepsilon_c \quad (14)$$

where; f_{co} , and, ε_{co} , are the peak stress and strain of the unconfined concrete, and, Δf_c , and, $\Delta \varepsilon_c$, are the enhancements in concrete strength and the corresponding strain due to lateral confinement, respectively.

The parameters primarily influencing the stress-strain relationship of confined concrete include the strength of concrete, yield strength of the confining reinforcement, volumetric ratio of the confining reinforcement to the concrete core as well as spacing between confining reinforcement, dimensions of the column, and the configuration of the lateral confining reinforcement. All these parameters are considered in the presented model. Table (1) presents the experimental work used in the analysis including 153 concrete specimens with different cross sections, heights, compressive strength, and transverse reinforcements.

Table 1: Experimental work included in the analysis

Author	Number of specimens	Shape	Cross section (mm)	Height (mm)	Compressive strength (MPa)	Transverse reinforcement %
Liu (2000)	12	Circular	D=250	1600	60- 96	0.58 – 3.18
Razvi (1999-b)	20	Circular	D= 250	1500	60 - 124	0.41 – 3.05
Pessiki (1997)	8	Circular	D=559	2235	37.9 – 84.7	1.32 – 2.61
Hoshikuma (1997)	11	Circular	D=200-500	600–1500	18.5 – 28.8	0.19 – 4.66
	13	Rectangular	D=200-1000	600- 1000	23.2 – 24.3	0.39 – 4.66
Saatcioglu (1998)	24	Rectangular	250	1500	60 - 124	0.99 – 4.59
Cusson (1994)	27	Rectangular	235	1400	52.6 – 115.9	1.40 – 4.80
Tan (1999)	18	Elliptical	258 - 644	1000	21.2 – 27.8	0.60 - 1.80
Schneider (1998)	3	Circular	141	635	23.8 – 28.1	CFST 3.0–6.68 mm
	11	Rectangular	76.6-152.8	635	23.8 – 30.4	CFST 3.0–7.47 mm
Shams (1999)	3	Circular	152.4	457-610	13.8 – 27.6	CFST 2.0-4.3 mm
	3	Rectangular	152.4	457-610	24.1 – 28.9	CFST 2.0-4.3 mm

Lateral Pressure

The strength capacity of concrete columns varies considerably with the amount and spacing of lateral confining reinforcement, and the strength of unconfined concrete. The lateral confining pressure in the case of confined circular columns can be easily quantified because the lateral pressure is almost uniform. For rectangular or elliptical column cross-sections, the distribution of the lateral confining pressure is not uniform. The configuration of the transverse reinforcement plays a big role in the behavior of such columns. Besides the variability in the confining pressure due to the shape of the cross section of the column, there is a variability of the pressure in the longitudinal direction due to the spacing between the hoops or the pitch of the spiral.

It is common to assume that when the concrete reaches its maximum resistance, the confining pressure can be computed by assuming that the lateral confining reinforcement yields as it was assumed by Cusson and Paultre (1995), Hoshikuma et al. (1997), and Razvi and Saatcioglu (1999-a). Saatcioglu and Razvi (1998) validated this assumption experimentally for the heavily confined high-strength concrete specimens with volumetric transverse reinforcement ratio of 1.3% for circular cross sections and 2% for rectangular cross sections. For lightly confined columns, the lateral reinforcement may not reach the yield strength but the assumption resulted in acceptable analytical results. In both cases, the consideration of the ratio of the concrete unconfined strength to the yield strength of lateral reinforcement needs to be included in the mathematical expression. A fine measurement for the effective lateral pressure at the maximum resistance can be calculated exploiting the following equation;

$$f_l = k_s k_f \rho_{st} f_{yt} \quad (15)$$

where; ρ_{st} , is the volumetric ratio of the transverse reinforcement to the confined concrete core and f_{yt} is the yield strength of the transverse reinforcement. Figure (1) shows the relationship between the lateral reinforcement ratio, ρ_{st} , and the enhancement in confined

concrete strength. The relationship is almost directly linear proportional with steady enhancement of concrete strength as the transverse reinforcement increase.

The coefficient, k_s , is induced to consider the effect of lateral pressure variability in the vertical direction. Figure (2) presents the relationship between spacing between transverse reinforcement to column breadth, s/b , and the enhancement in concrete compressive strength, f_{cc}/f_{co} . It is noticed from the figure that when, s/b , is less than 0.3 the enhancement gained

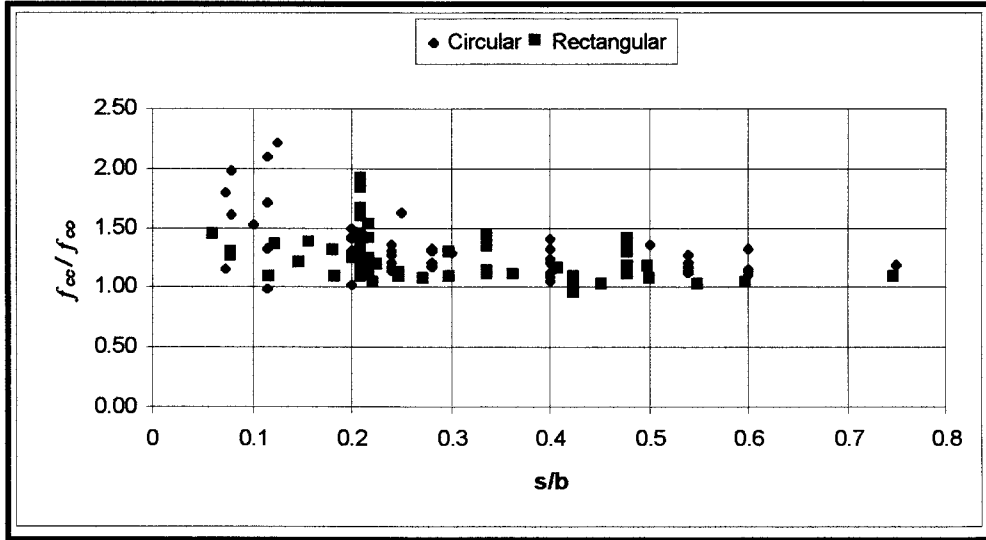


Figure 2: Relationship between spacing of transverse reinforcement to column breadth and the compressive strength enhancement

could be considerably higher considering all other affecting parameters. It was deduced in the analysis that columns with rectangular cross section are much more sensitive to the spacing of the lateral reinforcement than the columns with circular cross section. Hence, two different mathematical expressions are presented for this coefficient in the model;

$$k_s = \left(1 - \frac{s}{b}\right)^{0.5} \quad (16)$$

for circular cross sections and

$$k_s = \left(1 - \frac{s}{b}\right)^2 \quad (17)$$

for rectangular cross sections.

The coefficient, k_f , accounts for the change in confining pressure with the change in the ratio of unconfined concrete strength to yield strength of the lateral reinforcement. The factor applies the well-known phenomena that the higher concrete strength columns demand higher lateral reinforcement to obtain same properties enhancements. Figure (3) presents this effect on the enhancement in concrete strength, f_{cc}/f_{co} . It is observed clearly that when, f_{cc}/f_{co} , is less than 0.10 the enhancement in concrete strength could be impressive when other effective parameters are constant. The coefficient is calculated employing the following equation for both rectangular and circular cross sections;

$$k_f = 1 - \left(\frac{f_{co}}{f_{yt}}\right)^{0.5} \quad (18)$$

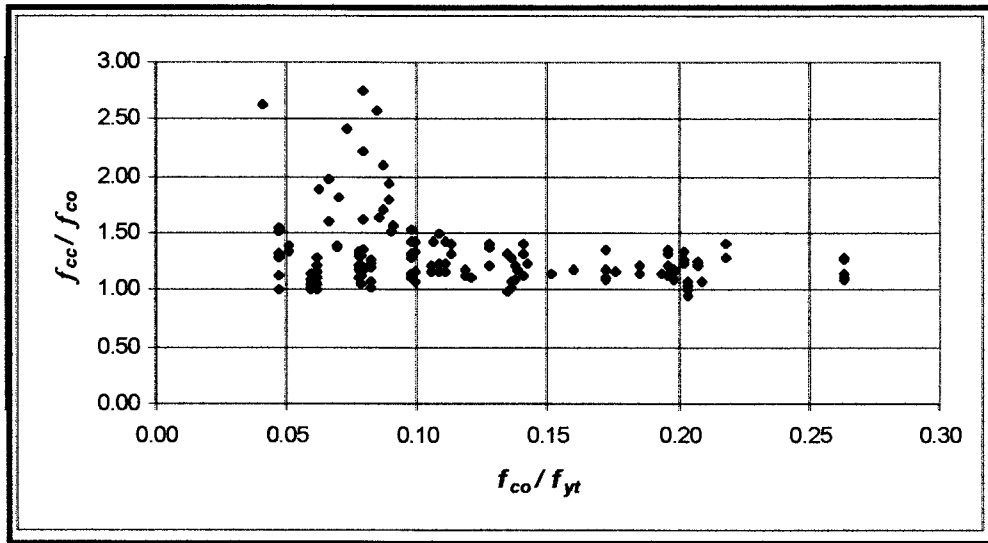


Figure 3: Relationship between concrete unconfined strength to yield strength of transverse reinforcement and the compressive strength enhancement

Peak Stress

It is shown in the previous sections and in Figures (1, 2, and 3) that peak stress of confined concrete columns depends primarily upon the strength of unconfined concrete, dimensions of confined core, and amount and configuration of the lateral reinforcement. For the computation of peak stress of normal and high-strength concretes, knowledge of unconfined concrete strength, f_{co} , and the effective lateral pressure, f_l , is needed. The response of confined concrete columns to the lateral pressure varies drastically by the change in the cross section. Columns with circular cross sections experience strength enhancement about double that experienced by columns with rectangular cross section when subjected to same lateral confining pressure. This is referred due the irregularity in the distribution of pressure on the cross section of the rectangular columns. Hence, the following relationship are derived after excessive mathematical calibrations for different types of expressions to represent the confined concrete strength in terms of its unconfined strength and the applied lateral confining pressure;

The following relationship is utilized to predict the compressive strength of confined concrete columns;

$$f_{cc} = f_{co} + 3.8 f_l \quad (19)$$

for circular cross sections and

$$f_{cc} = f_{co} + 1.8 f_l \quad (20)$$

for rectangular cross sections. The results of the elliptical concrete columns included in the analysis show mechanical response to the lateral confinement that is similar to that of the rectangular columns.

Figure (4) shows the relationship between the experimentally recorded results for the confined concrete strength versus the values derived analytically from the proposed model. The correlation between the two sets of values is terrific for most of the specimens. The calculated, R^2 , value is 0.946 that displays the fine matching between experimental and analytical results.

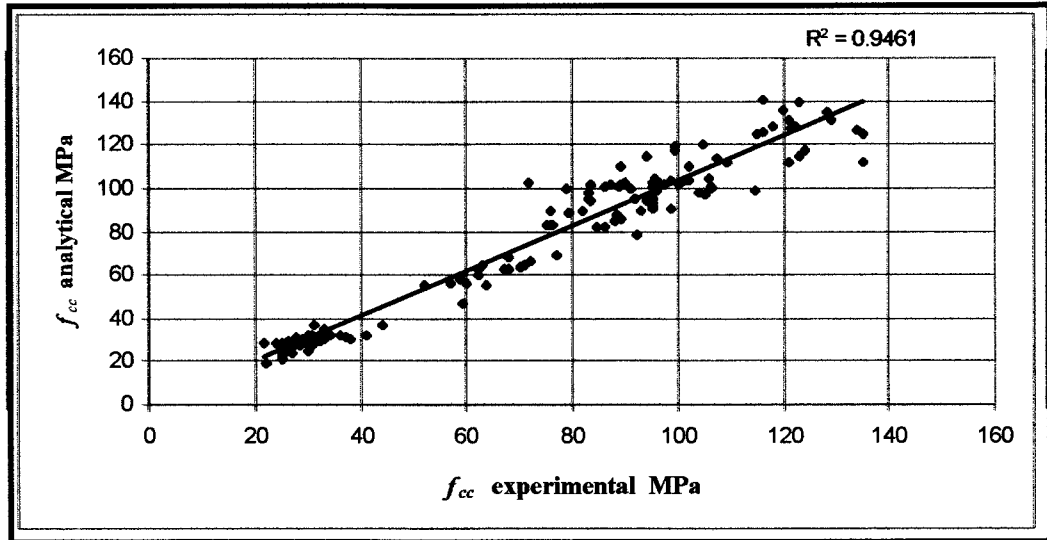


Figure 4: Correlation between experimental and analytical concrete confined strength

Peak Strain

The results obtained experimentally for confined concrete specimens proved that high-strength concrete columns require a considerably higher level of lateral confining pressure to simulate the same ductility enhancements of normal strength concrete columns. The variation in the recorded peak strain values is dramatic from one research to another which can be referred to the mix proportions, age of concrete at testing, additive used in the mix, and type of aggregate utilized in the specimen. These parameters are not included neither in the presented study nor in any previous one because of difficulties of quantification of these influences. Records of Razvi and Saatcioglu (1999-b), and Saatcioglu and Razvi (1998) shows considerably lower peak strains than those recorded by, Cusson and Paultre (1994) and Hoshikuma et al. (1997) for the same concrete strength, dimensions, and transverse reinforcement quantity and configuration. Results obtained by Liu et al. (2000) showed very high values for the peak strain of the confined columns so that it is excluded from the analytical derivation for the peak strain expression.

Figure (5) shows general relationship between the confining pressure ratio to the unconfined strength, f_l / f_{co} , and the peak strain of the experimented specimens. The figure illustrates the proportionality of the confining pressure with the peak strain value in general but a wide scatter can be easily noticed in the figure due to the reasons mentioned earlier. After considerable trials, the following mathematical relationship is found to best fit the relationship between the strain at peak stress value and the effective lateral pressure, f_l / f_{co} . The relationship is:

$$\varepsilon_{cc} = \varepsilon_{co} + 0.57 \left(\frac{f_l}{f_{co}} \right)^3 \quad (21)$$

where the peak strain of the unconfined concrete, ε_{co} , is expressed as per the recommendation of Shah and Ahmad (1994);

$$\varepsilon_{co} = 0.00165 + 0.0000165 f_c' \quad (22)$$

The peak strain mathematical expression has an, R^2 , value of 0.714 with respect to the recorded values for the experimental results.

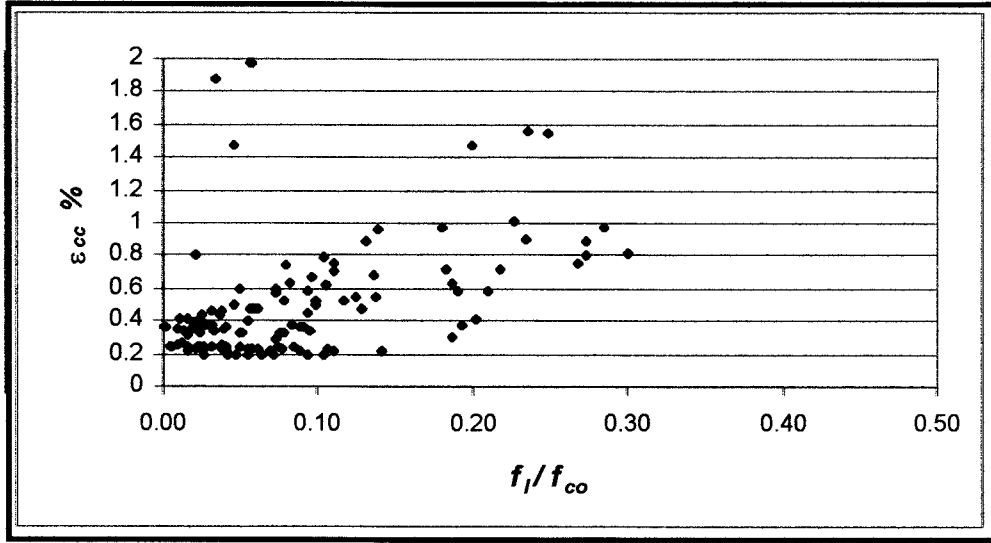


Figure 5: Relationship between ratio of lateral confining pressure to concrete compressive strength and peak strain

Descending Branch

The shape of the post-peak portion of the stress-strain curves is primarily governed by the parameter, B , in the fractional equation (10). To calculate the value of this parameter, a post-peak point is needed to be established. The point at 85% or 50% of the confined concrete strength in the post-peak portion of the curve can be utilized as this reference point. The 85% strength post-peak point is preferred to be used for low strength concrete and well-confined specimens since the descending portion should not have steep descending curve. On the contrary, columns with high-strength concrete and low to medium confinement are sensitive to the strain beyond the peak point. Hence, the point at 50% strength has a good representation for the post-peak portion of the later type. It has an intermediate location on the descending portion, far from the sensitivity zone near the peak point, and ahead of the collapse of the specimen.

A detailed investigation was carried out to find an appropriate mathematical equation that would represent the strain of concrete at 85% and 50% of the peak strength, ϵ_{85} and ϵ_{50} , respectively. The strains of concrete in the post-peak portion of the response, ϵ_{85} and ϵ_{50} , are found to be correlated to the strength of confined concrete more than to the strength of unconfined strength. Based on the experimental records, the following expressions are found to be most representative of the test data:

$$\epsilon_{50} = \epsilon_{cc} + 0.033 \left(\frac{f_l}{f_{cc}} \right)^{0.5} \quad (23)$$

and

$$\epsilon_{85} = \epsilon_{cc} + 0.021 \left(\frac{f_l}{f_{cc}} \right)^{0.5} \quad (24)$$

The above-mentioned mathematical expressions have, R^2 , values of 0.93 and 0.73, respectively, with respect to the experimental results included in the study. Once the reference point, ϵ_{85} or ϵ_{50} , is established, the parameter, B , can be obtained by back substitution in equation (10). It shows as;

$$B = \frac{1 - Ax - 2x + 2x^2}{x^2} \quad (25)$$

where; x , is used as for ϵ_{85} or ϵ_{50} .

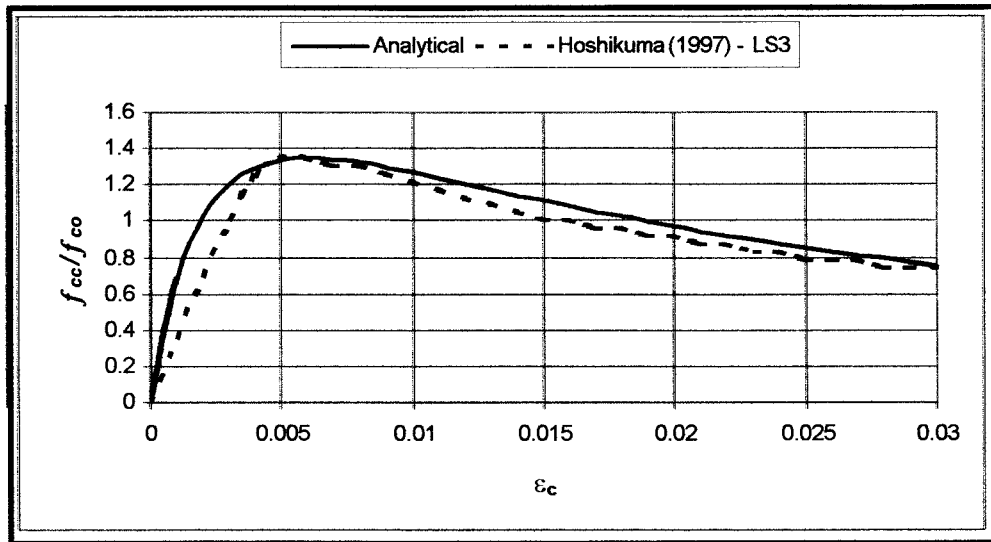


Figure 6: Analytical vs. experimental stress-strain relationship for LS-3 specimen tested by Hoshikuma et al. (1997)

Verification of Model

Comparisons between the complete stress-strain curves predicted by the proposed model and the experimental results are shown in Figures (6) and (7). Figure (6) shows the results for a square column of 500 mm side length and 1,000 mm height. The specimen was confined by 13 mm diameter welded hoops spaced at 40 mm intervals. The volumetric ratio of the transverse reinforcement was 2.6%. The unconfined compressive strength of concrete was 24.3 MPa and the yield strength of the hoops was 295 MPa. Figure (7) presents the results for a square column of 235 mm side length and 1,400 mm total height. The specimen was confined by 9.5 mm diameter hooked hoops spaced at 50 mm intervals. The volumetric ratio of the transverse reinforcement was 2.8%. The unconfined compressive strength of concrete was 99.9 MPa and the yield strength of the hoops was 705 MPa.

The figures show the effect of lateral confinement on the behavior of concrete columns with respect to the unconfined concrete strength. The lateral confining pressure for the specimen shown in Figure (6) is 4.63 MPa versus 7.99 MPa for the specimen shown in Figure (7). Despite that the lateral pressure for the first specimen is less than the second one, it experienced higher strength and ductility enhancements because its unconfined strength is much less than the second one. In both cases, the proposed model demonstrated high predictive capacity for different values of unconfined concrete strength, cross sectional dimensions, yield strength of transverse reinforcement, and spacing of hoops.

It could be noticed by comparison for the behavior of normal strength and high strength concrete columns that for comparable specimens, the higher strength concrete specimens have lower deformability and energy absorption and dissipation capacities initially. During the latter part of the displacement excursions, these properties improve rapidly and the total values are comparable to those of lower strength concrete specimens. The same conclusion was reported by Bayrak and Sheikh (1998).

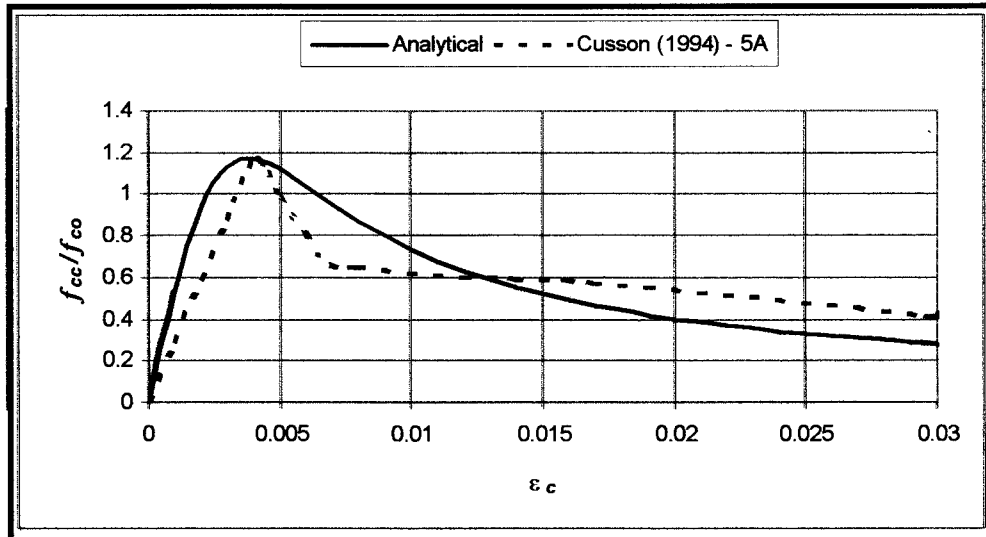


Figure 7: Analytical vs. experimental stress-strain relationship for 5-A specimen tested by Cusson & Paultre (1994)

CONCRETE-FILLED STEEL TUBES

A polynomial equation representing 3D cross-section strength of square or rectangular concrete-filled steel tube (CFST) was presented by Hajjar and Gourley (1996). The equation was based mainly on two parameters; 1) width to thickness ratio of the tube and 2) the ratio of the concrete compressive strength to the yield stress of the tube. The model is simple but difficult to compare or incorporate with other models for columns confined by hoops.

Concrete-filled steel tubes are represented in this study by the experimental results obtained by Schneider (1998) and Shams and Saadeghvaziri (1999). The ratio between the diameter of the specimen or its side length to the thickness of the tube, D/t , is one of the most important parameter in the CFST behavior. The first one included results for column specimens with, D/t , ratio ranging from 17.0 to 50.8 while the second one included specimens with, D/t , ratio from 10 to 100. Both studies included circular and rectangular cross sections. The, D/t , ratio is corresponding to the volumetric transverse reinforcement ratio for the tied column specimens.

The behavior of concrete-filled steel tubes is similar to that recorded for columns confined by spirals or ties. Almost all parameters included in the numerical model for the stress-strain relationship for confined concrete are applicable for the CFST specimens. The only difference in the modeling is found in the evaluation of the confined concrete strength. It is noticed that for CFST with circular cross sections, the following mathematical expressions are applied;

$$f_{cc} = f_{co} + 3.0 f_l \quad (26)$$

for circular cross sections and

$$f_{cc} = f_{co} + 1.8 f_l \quad (27)$$

for rectangular cross sections.

A limitation for the thickness of tubes that assure the yield stress of the steel is reached. In most of the cases studied herein, the steel did not reach its yield strength. Hence, the confinement applied to the concrete was less than that obtained traditionally for cases with less thickness of steel tube. Further investigation for high-strength CFST is required to evaluate the behavior with this type of concrete. It is expected that higher concrete strength will require less, \bar{D}/t , ratio to develop the same level of strength and ductility as that experienced by normal strength concrete tested in the two considered studies.

PRACTICAL APPLICATION

The confinement of concrete columns has a neglect effect on strength and ductility up to 40-50% of the compressive strength. The real benefit from confinement arises when the applicable load is close to the concrete strength or beyond this limit. The later situation does not exist in ordinary working stage of loading but may be born as a result of seismic load or extraordinary situation of loading. The parameter, $\rho_{st} f_{yt} / f_{co}$, was used in ACI-ASCE Committee 441 (1997) as a guidance measure for the confinement.

Saatcioglu and Razvi (1998) proposed a minimum value of 0.18 for the term, $\rho_{st} f_{yt} / f_{co}$, for columns with rectangular cross section. Also, Razvi and Saatcioglu (1999-b) proposed a minimum value of 0.09 for the same term for concrete columns with circular cross sections. Based on the extensive study carried out in the research, it was reached that a value of 0.10 for, $\rho_{st} f_{yt} / f_{co}$, for circular columns most probably results in 20% strength enhancement and ductility index ($\epsilon_{50} / \epsilon_{cc}$) of 3. Also, a value of 0.15 for the same term with rectangular columns may result in 10% strength enhancement and ductility index of 3. The lately mentioned values are recommended for columns severely exposed to quakes or similar cases.

CONCLUSIONS

A numerical model is presented to predict the stress-strain relationship for normal and high strength concrete columns of rectangular and circular sections confined with spirals, ties, cross ties, or continuous tubes (concrete-filled steel tubes). The model is based on the experimental results of 153 concrete specimens subjected to different types and amounts of transverse reinforcement and tested under concentric loading. Comparisons are made between the predictions of the model and the available experimental results. It can be concluded from the study that:

- The model demonstrates good predictive capability and is applicable for a wide range of variables that include range of unconfined concrete strength from 20 MPa to 120 MPa and transverse reinforcement ratio from 0.2% to 4.9% by volume.
- The strength enhancement, f_{cc} / f_{co} , of the confined concrete decreases with the increase of concrete strength but the total absorbed energy by the column increases with the same strength and lateral confinement configuration.
- The ductility of the confined columns decreases drastically with the increase of concrete strength for the same confinement pattern. Equation (21) shows the exponential relationship between the peak strain and unconfined concrete strength.
- It is realized that a value of 0.10 for, $\rho_{st} f_{yt} / f_{co}$, for circular columns most probably results in 20% strength enhancement and ductility index ($\epsilon_{50} / \epsilon_{cc}$) of 3. Also, a value of 0.15 for the same term with rectangular columns may result in 10% strength enhancement and

ductility index of 3. The lately mentioned values are recommended for columns severely exposed to quakes or similar cases.

- The concrete-filled steel tube (CFST) specimens show stress-strain relationship that is similar to that of column specimens confined with ties or hoops. The traditional, D/t , relationship that controls the prediction of lateral confinement in CFST can be adjusted to match the mathematical expressions of traditionally confined concrete columns. It is needed to have more results for high-strength CFST to analyze the behavior this type of concrete when confined by tubes.

NOTATIONS

E_c	Modulus of elasticity
E_p	Plastic modulus
E_{des}	Deterioration rate
b	Smaller side of column or diameter
f_c	concrete stress
f'_c	specified concrete strength
f_{cc}	confined concrete strength
f_{co}	unconfined concrete strength
f_l	lateral pressure
f_{yt}	yield strength of lateral reinforcement
$k, k_1, \text{ and } k_2$	constants
s	Spacing between hoops
w_c	Unit weight of concrete
ε_c	concrete strain
ε_{cc}	Confined concrete strain at peak point
ε_{co}	Unconfined concrete strain at peak point
ε_{50}	Concrete strain at 50% of the confined strength on the post-peak branch
ε_{85}	Concrete strain at 85% of the confined strength on the post-peak branch
ρ_{st}	Volumetric ratio of lateral reinforcement to concrete core

REFERENCES

- Van Mier, J. G. M., (1986) "Fracture of Concrete under Complex Stress", HERON, Delft University of Technology, Netherlands.
- Karabinis, A. I. And Kiouisis, P. D., (1994), "Effects of Confinement on Concrete Columns: Plasticity Approach", *Journal of Structural Engineering*, ASCE, 120 (9), pp. 2747-2767.
- Cusson, D. and Paultre, P., (1995), "Stress-Strain Model for Confined High-Strength Concrete", *Journal of Structural Engineering*, ASCE, 121 (3), pp. 468-477.
- Liu, J., and Foster, S. J., (1998), "Finite-Element Model for Confined Concrete Columns", *Journal of Structural Engineering*, ASCE, 124 (9), pp. 1011-1017.
- Foster, S. J., Liu, J., and Sheikh, S. A., (1998), "Cover Spalling in HSC Columns Loaded in Concentric Compression", *Journal of Structural Engineering*, ASCE, 124 (12), pp. 1431-1437.
- Mau, S. T., Elwi, A. E., and Zhou, S. Z., (1998), "Analytical Study of Spacing of Lateral Steel and Column Confinement", *Journal of Structural Engineering*, ASCE, 124 (3), pp. 262-269.

- Hoshikuma, J., Kawashima, K., Nagaya, K., and Taylor, A. W., (1997), "Stress-Strain Model for Confined Reinforced Concrete in Bridge Piers", *Journal of Structural Engineering*, ASCE, 123 (5), pp. 624-633.
- Razvi, S. R. and Saatcioglu, M., (1999-a), "Confinement Model for High-Strength Concrete", *Journal of Structural Engineering*, ASCE, 125 (3), pp. 281-289.
- Sargin, M., Ghosh, S. K., and Handa, V. K., (1971) "Effects of lateral reinforcement upon the strength and deformation properties of concrete", *Magazine of Concrete Research*, Vol. 23, No. 75-76, pp. 99-110.
- Ahmad, S. H., and Shah, S. P., (1982), "Complete Triaxial Stress-Strain Curves For Concrete", *Journal of Structural Engineering*, ASCE, V. 108, No. ST 4, pp. 728-742.
- Martinez, S., Nilson, A. H., and Slate, F. O., (1984), "Spirally Reinforced High-Strength Concrete Columns", *ACI Journal, Proceedings*, September-October, pp. 431-442.
- ACI Committee 318, (1995), "Building Code Requirements for Reinforced Concrete and Commentary (ACI 318-95/ ACI 318R-95)", American Concrete Institute, Detroit.
- Cusson, D. and Paultre, P., (1994), "High-Strength Concrete Columns Confined by Rectangular Ties", *Journal of Structural Engineering*, ASCE, 120 (3), pp. 783-804.
- Liu, J., Foster S. J., and Attard, M. M. (2000), "Strength of Tied High-Strength Concrete Columns Loaded in Concentric Compression", *ACI Structural Journal*, V. 97, No. 1, pp. 149-156.
- Razvi, S. R. and Saatcioglu, M., (1999-b), "Circular High-Strength Concrete Columns under Concentric Compression", *ACI Structural Journal*, V. 96, No. 5, pp. 817-825.
- Pessiki, S. and Pieroni, A., (1997), "Axial Load Behavior of Large-Scale Spirally-Reinforced High-Strength Concrete Columns", *ACI Structural Journal*, V. 94, No. 3, pp. 304-314.
- Saatcioglu, M. and Razvi, S. R., (1998), "High-Strength Concrete Columns with Square Sections under Concentric Compression", *Journal of Structural Engineering*, ASCE, 124 (12), pp. 1438-1447.
- Tan, T. H., and Yip, W. K., (1999), "Behavior of Axially Loaded Concrete Columns Confined by Elliptical Hoops", *ACI Structural Journal*, V. 96, No. 6, pp. 967-971.
- Schneider, S. P. (1998), "Axially Loaded Concrete-Filled Steel Tubes", *Journal of Structural Engineering*, ASCE, 124 (10), pp. 1125-1138.
- Shams, M. and Saadeghvaziri, M. A., (1999), "Nonlinear Response of Concrete-Filled Steel Tubular Columns under Axial Loading", *ACI Structural Journal*, V. 96, No. 6, pp. 1009-1017.
- Shah, S. P. and Ahmad, S. H. (1994), "High Performance Concrete: Properties and Applications", McGraw-Hill, Inc.
- Bayrak, O. and Sheikh, S. A., (1998), "Confinement Reinforcement Design Considerations for Ductile HSC Columns", *Journal of Structural Engineering*, ASCE, 124 (9), pp. 999-1010.
- ACI-ASCE Committee 441 (1997), "High-Strength Concrete Columns: State of the Art", *ACI Structural Journal*, V. 94, No. 3, pp. 323-335.
- Hajjar, J. F., and Gourley, B. C. (1996), "Representation of Concrete-Filled Steel Tube Cross Section Strength", *Journal of Structural Engineering*, ASCE, 122 (11), pp. 1327-1336.